

 BÖHLER

EDRO



PLASTIC
MOULD STEEL


HIGH PERFORMANCE MOLD STEELS FOR INJECTION OF REINFORCED PLASTICS

exclusively distributed in the USA by EDRO Speciality Steels

HIGH PERFORMANCE MOLD STEELS FOR INJECTION OF REINFORCED PLASTICS

Modern industrial parts production in mainly automotive and electronic industries is characterized by the trend to substitute metals by reinforced plastics. Being much lighter and therefore weight-saving, such plastic components help to reduce CO₂ emissions, which is a clear ecologic focus worldwide. Intricate geometries, thin wall-thicknesses and large areas of the parts are characteristics that call for a growing amount of glass or carbon fibers in the plastics to obtain sufficient stability.

Plastics reinforced by fibers tend to be much more abrasive than conventional plastics and thus may cause premature wear of an injection mold. In order to counteract excessive and early wear in molds, voestalpine BÖHLER Edelstahl is offering a wide variety of high-quality tooling steels that are setting new standards in the production of heavy-duty components made from reinforced plastics.

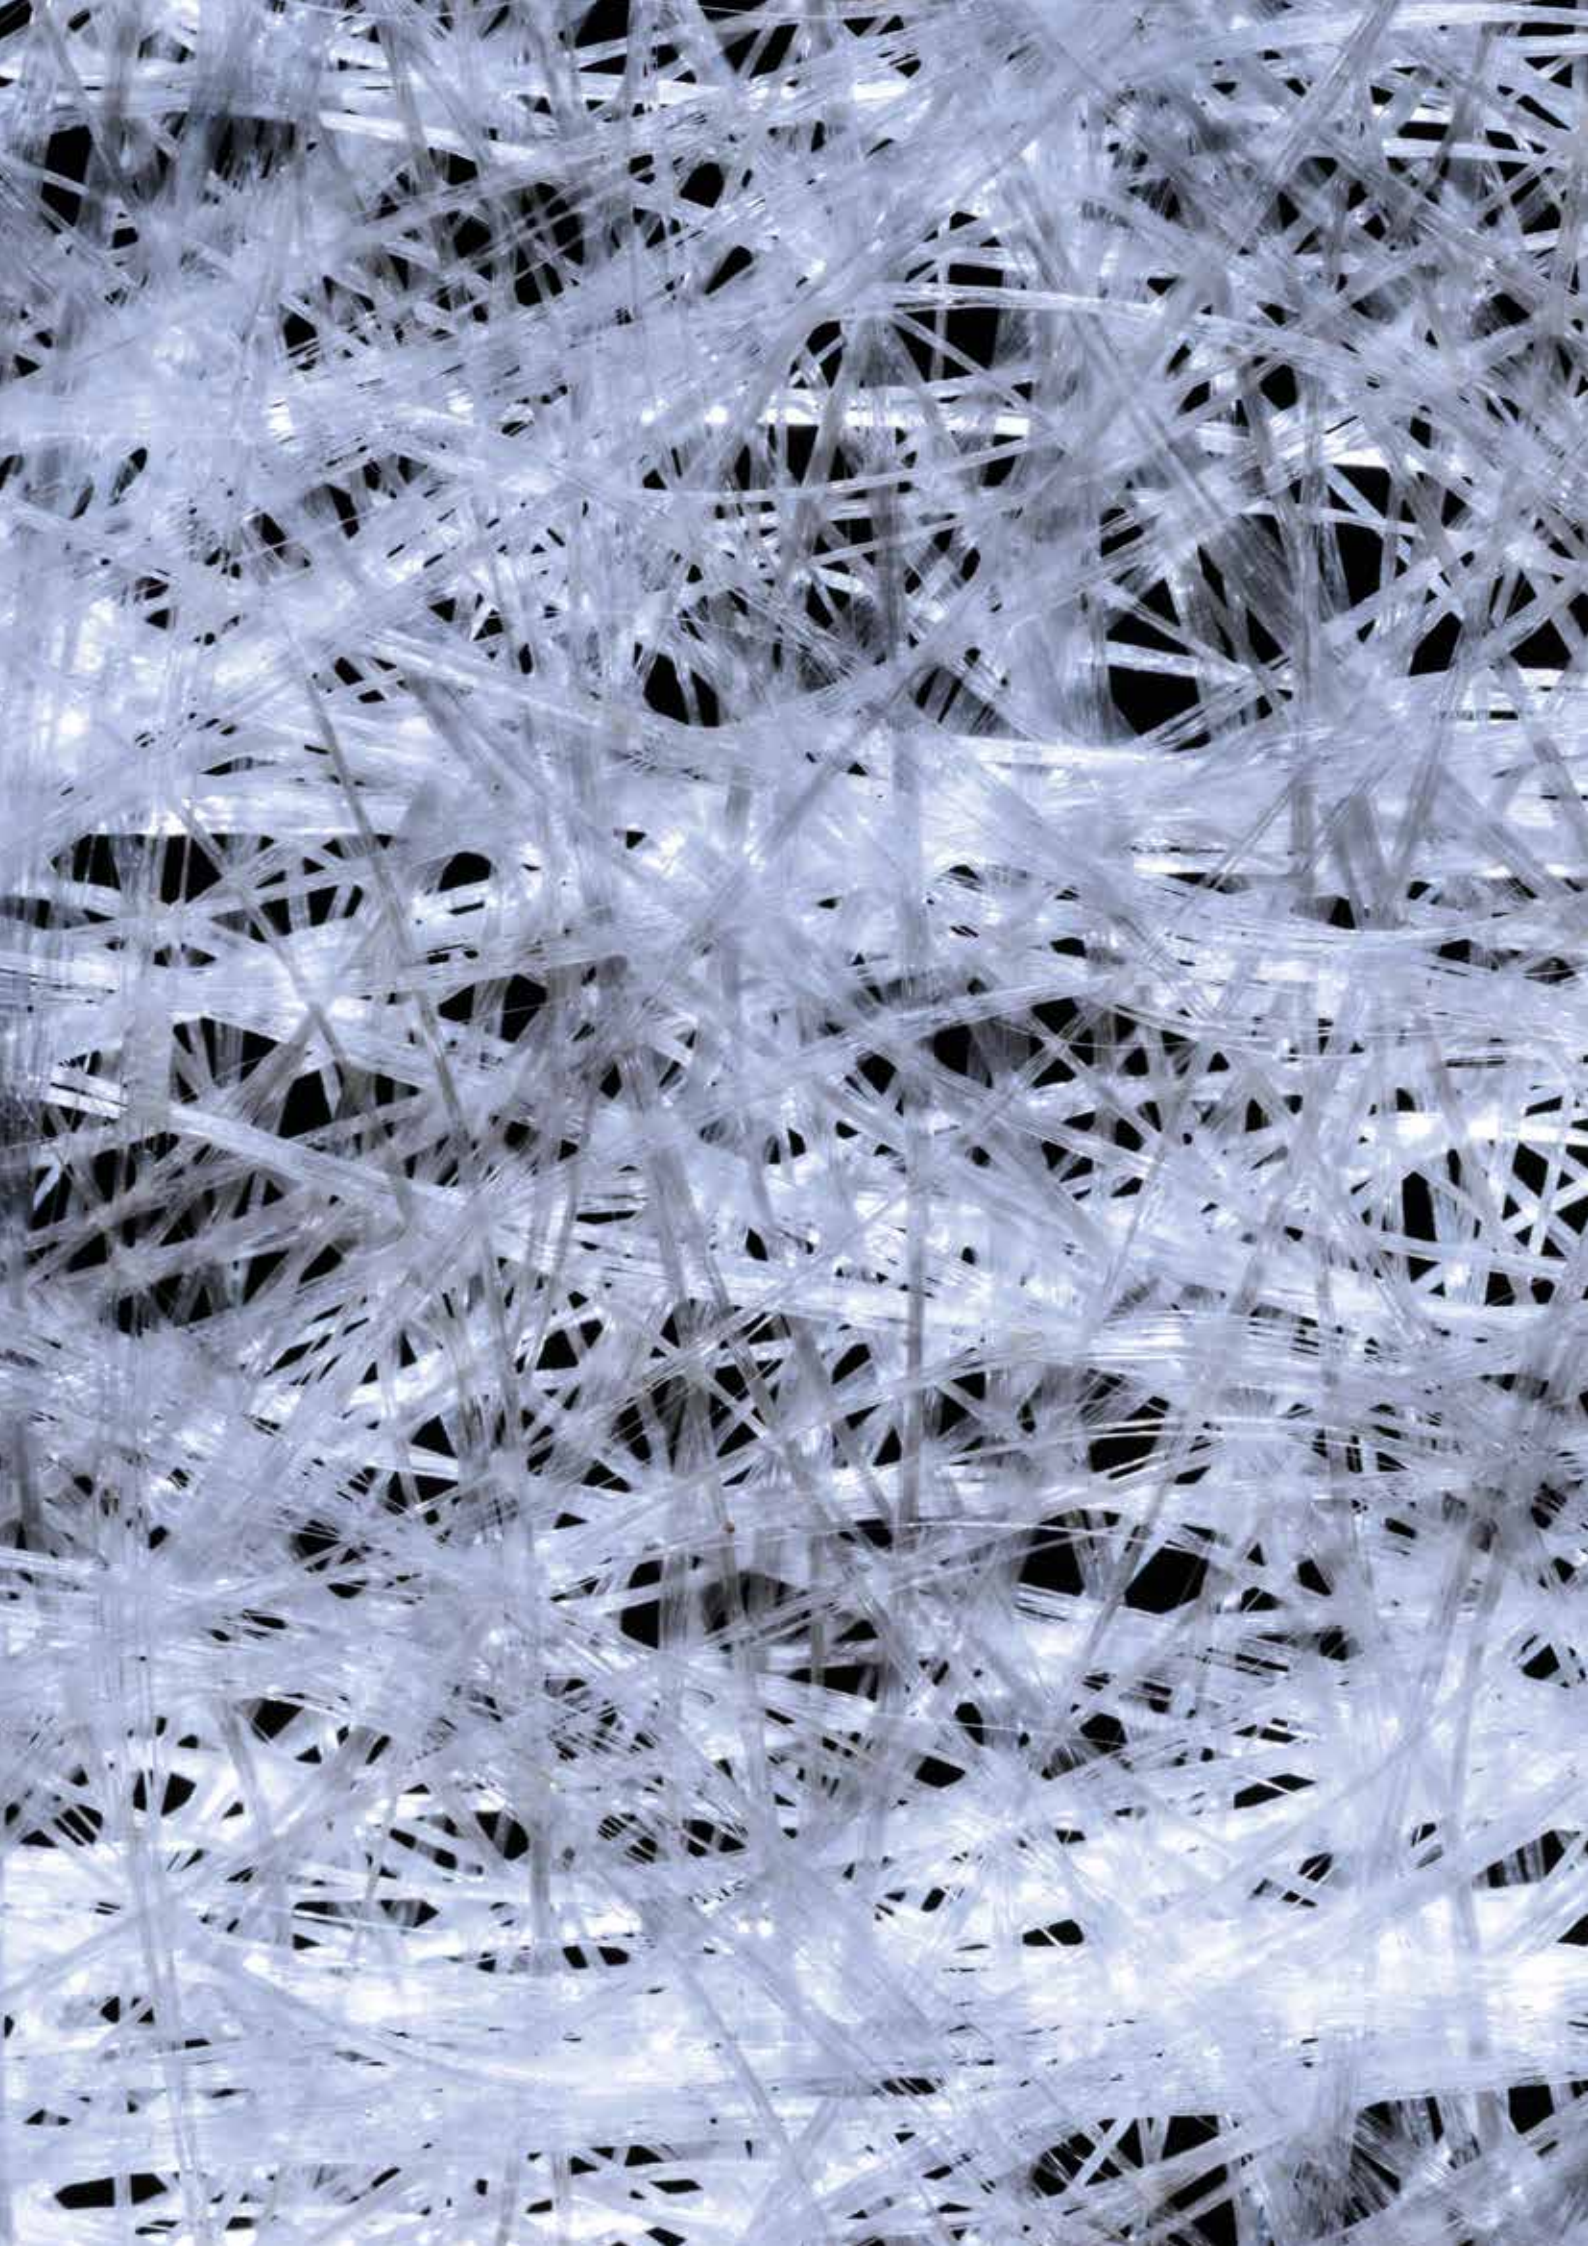

TRENDS AND REQUIREMENTS

- » New types of high performance plastics (GF, CF, fibre length, filler material)
- » Increasing wear resistance requirements on mold material
- » Increasing corrosion resistance of mold material
- » Complexity of parts increased (light weight construction)
- » Increase productivity through shorter cycle times (thermal conductivity)
- » Higher closing pressures and processing temperatures

PLASTIC MOLDING

EXAMPLE OF „POLYMERIC LEIGHT WEIGHT CONSTRUCTION“



Prototype:
Plastic steering case

- » Equal cost part made of 50% glass fiber reinforced PA (Ultramid® A3R) with metal inserts
- » Special FEM –Design modification
- » Service temperature: max. 125 °C
- » **50% weight savings**

Source: ThyssenKrupp techforum 1/2014



Steering casing
Al- HPDC part
(Symbolic picture)

PLASTIC PROCESSING

SELECTED PARTS/COMPONENTS MADE OF LONG FIBER REINFORCED THERMOPLASTIC



Long glass-fiber reinforced car frontend
Source: M. Schemme, FH Rosenheim



Long-fiber reinforced door module
Source: M. Schemme, FH Rosenheim



Short glass-fiber reinforced brake/clutch pedal holder
Source: POLYCOM



Oilpan
Source: LANXESS

HIGH PERFORMANCE PLASTICS

AUTOMOTIVE



PA6 - GF65



PA66 - CF35

HOUSEHOLD



PA66 - CF35




PC+ABS - GF40



PA6 - GF40


PLASTICS PYRAMID

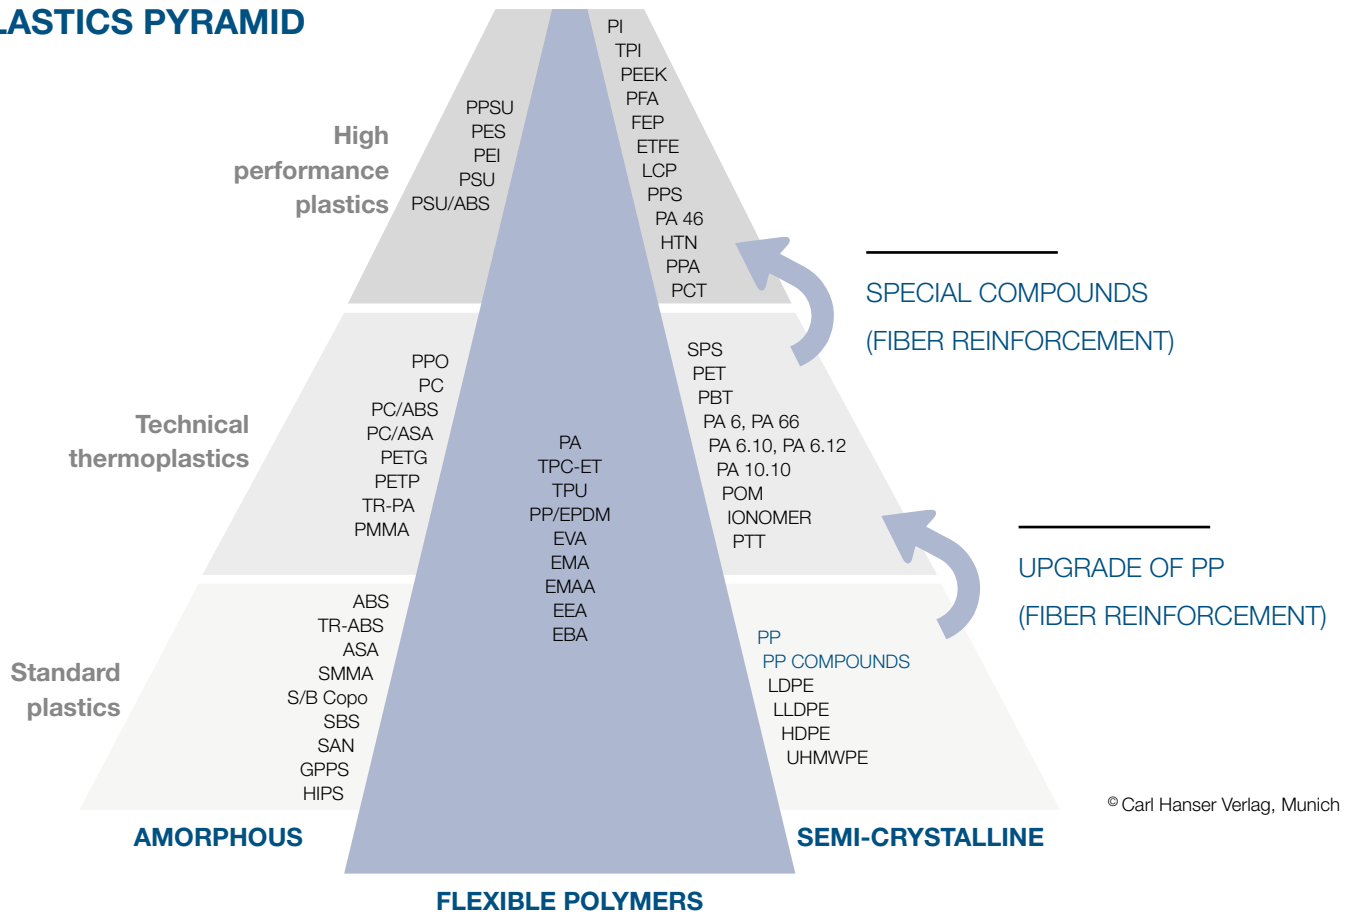

© Carl Hanser Verlag, Munich

WEAR MECHANISM

Fiber motion causes abrasive wear by

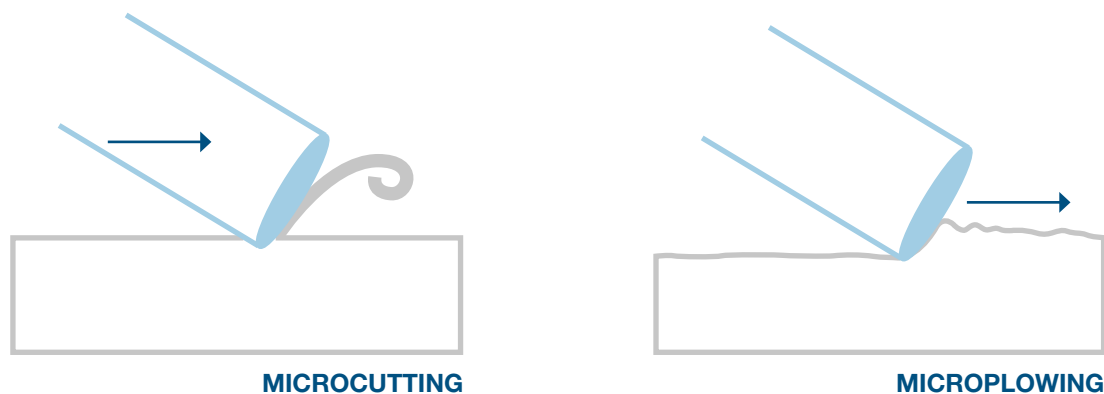


Beside glass fibers also glass balls, metal oxides (titanium oxide, chromium oxide), calcium carbonates, silica components (sand, quartz), ceramics are forcing abrasive wear.

Source: Department of Injection Moulding of Polymers, University of Leoben

INFLUENCING FACTORS

Fiber Length

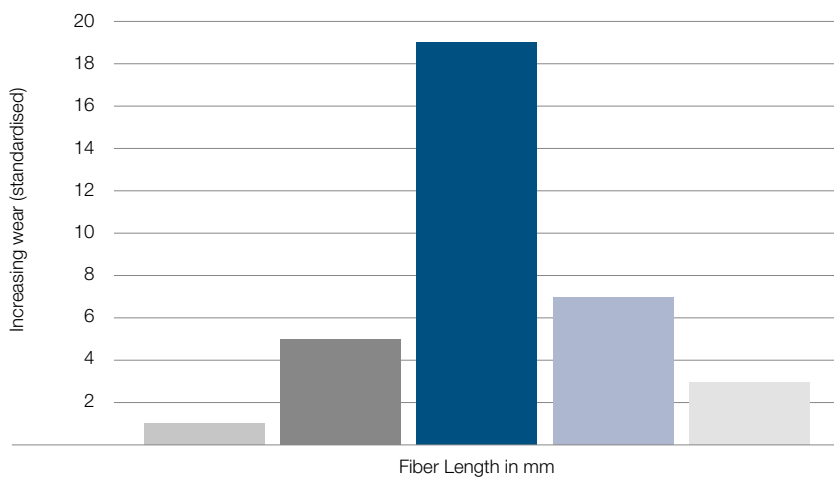


Typical fiber diameter: 10 µm

- Length up to 200 µm
- 200 µm < L < 500 µm
- 500 µm < L < 1000 µm
- 1000 µm < L < 2000 µm
- Length > 2000 µm


Source:
Department of Injection
Moulding of Polymers,
University of Leoben

Polymer melt with glass fibers

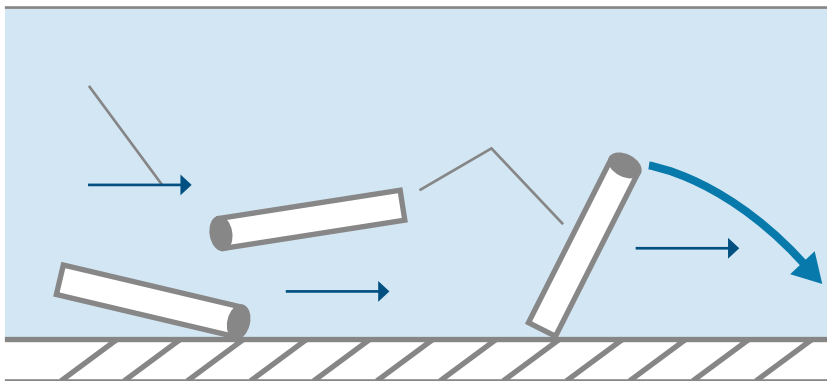

PRODUCT SELECTION – HIGH PERFORMANCE MOLD STEELS

Non corrosion resistant steels

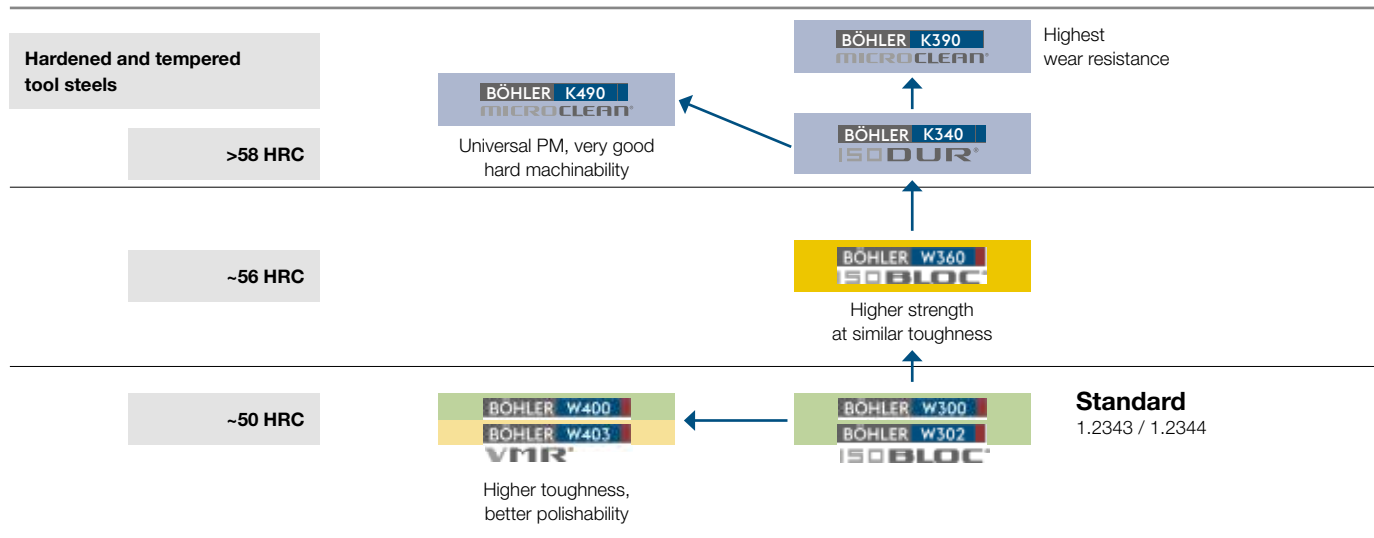

- up to ~20% GF
- up to ~30% GF
- up to ~60% GF
- up to ~65% GF

Examples for processed plastics
 PA6 - GF50
 PA66 - GF40
 PA66 - GF35
 PA66 - GF30
 PC+ABS-GF40
 POM - CF35
 PA6 - GF65
 PA6 - CF45

MICROCLEAN®

Powder metallurgical steels

VMR®

Special materials subjected to vacuum refining or melting during at least one stage of manufacture.

ISODUR®


Cold work tool steels in ESR quality

ISOBLOC®

Hot work tool steels in ESR quality with special heat treatment

BÖHLER grade	Chemical composition in weight %						Standard	Carbide vol-[%] hardened	Wear resistance
	C	Cr	Mo	V	W	Others			
BÖHLER W300 ISOBLOC	0.4	5.0	1.3	0.4	–	–	1.2343 / H11	< 1	★
BÖHLER W302 ISOBLOC	0.4	5.2	1.4	1.0	–	–	1.2344 / H13	< 1	★
BÖHLER W400 VMR	0.4	5.0	1.3	0.5	–	–	1.2340 / ~H11	< 1	★
BÖHLER W403 VMR	0.4	5.0	2.8	0.7	–	–	1.2367	< 1	★
BÖHLER W360 ISOBLOC	0.5	4.5	3.0	0.6	–	–	–	< 1	★★
BÖHLER K340 ISODUR	1.1	8.3	2.1	0.5	–	+Al, Nb	–	8.5	★★★
BÖHLER K490 MICROCLEAN	1.4	6.4	1.5	3.7	3.5	+ Nb	–	10	★★★★
BÖHLER K390 MICROCLEAN	2.5	4.2	3.8	9.0	1.0	+ 2.0 Co	–	17	★★★★★

Corrosion resistant steels (minimum free chromium content in the matrix of 13 %)

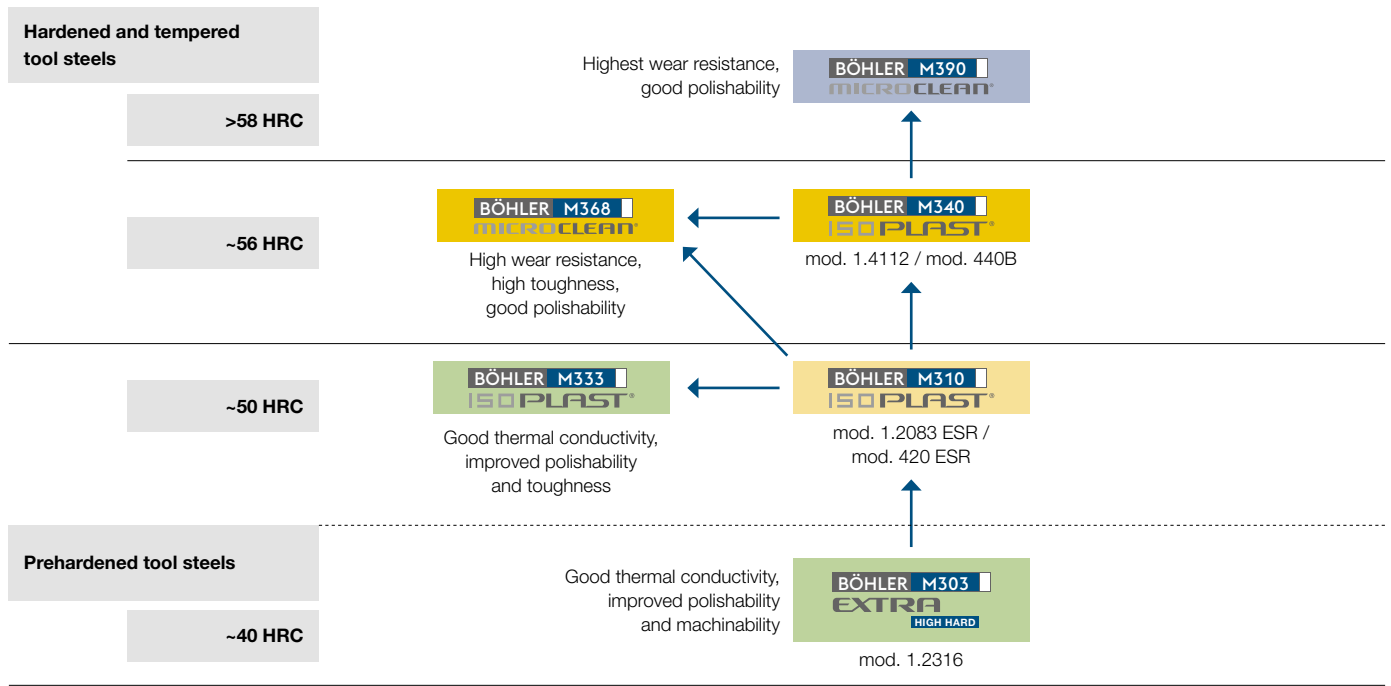

- up to ~10% GF
- up to ~15% GF
- up to ~60% GF
- up to ~65% GF

Examples for processed plastics
PVC, CPVC, PES, PSU, PVDF, ABS


MICROCLEAN[®]
Powder metallurgical steels

ISOPLAST[®]
Plastic mould steels in ESR quality

EXTRA
Special property and/or achievement characteristics

BÖHLER grade	Chemical composition in weight %						Standard	Carbide vol.-% hardened	Wear resistance
	C	Cr	Mo	Ni	V	Others			
BÖHLER M303 EXTRA HIGH HARD	0.27	14.50	1.00	0.85	-	+N	~1.2316	< 1	★
BÖHLER M333 ISOPLAST	0.24	13.25	+	+	+	+N	~1.2083 / ~420	< 1	★★
BÖHLER M310 ISOPLAST	0.38	14.30	-	-	0.20	-	~1.2083 / ~420	1.5	★★
BÖHLER M340 ISOPLAST	0.54	17.30	1.10	-	0.10	+N	-	ca. 8%	★★★
BÖHLER M368 MICROCLEAN	0.54	17.30	1.10	-	0.10	+N	-	ca. 8%	★★★
BÖHLER M390 MICROCLEAN	1.90	20.00	1.00	-	4.00	W=0.60	-	ca. 20%	★★★★★

HEAT TREATABLE, WEAR RESISTANT MOLD STEEL

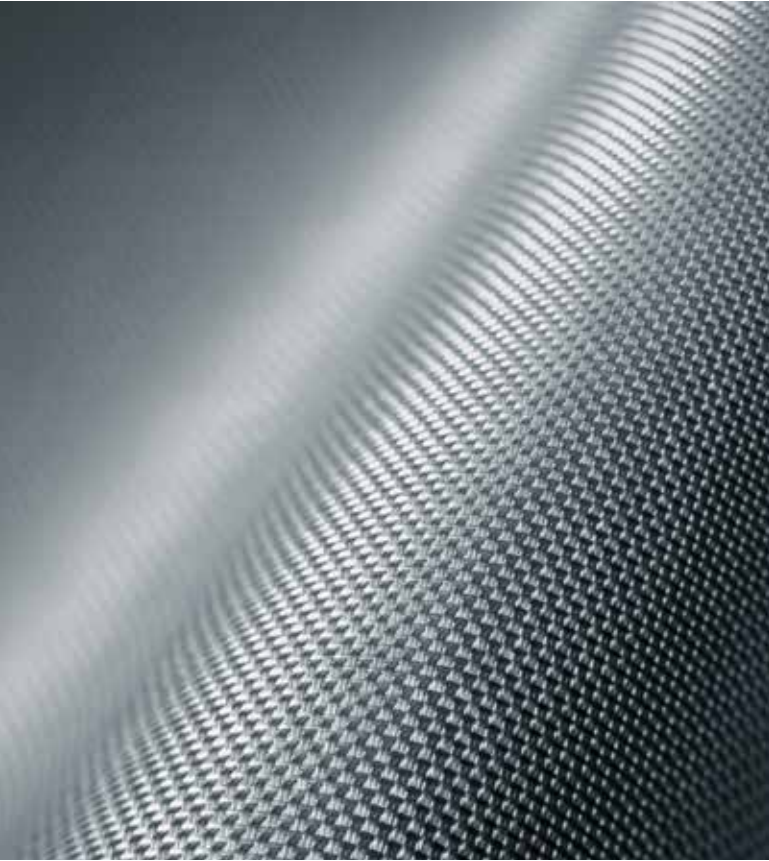


The wear is determined either by mass loss or volumetrically by 3D measurement of the sample surfaces before the test and after injection of, for example, 25 kg or 50 kg of glass fiber reinforced plastic molding compound.


The wear apparatus for testing the abrasive/corrosive wear on the tribosystem polymer melt/steel is installed in the injection molding machine in the form of an injection molding tool. The wear samples, which have the same temperature as the melt, form a rectangular gap in which large local shear stresses and shear rates can be generated. The melt is injected through the wear gap and generates the material removal on the surfaces of the two wear samples (each 15 x 12 x 5 mm). The entire dosing volume of the plasticized molding compound is injected at a defined injection pressure, defined injection rate and a specified melt temperature.

The wear is determined by the material removal (mg/cm^2) or the material removal height (μm) before and after injected a defined amount of plastic melt.

Small Plates Wear Tests

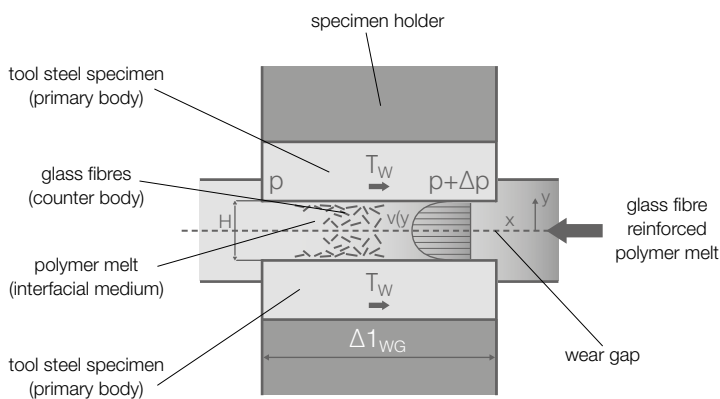


Mean depth of abrasion or weight loss of the testing plates indicates the wear resistance.

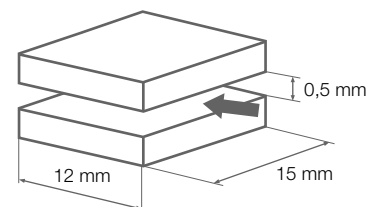


EFFECT OF CORROSION AND ABRASION – LABORATORY TEST RESULTS K110 VS. M390 MICROCLEAR, RESULTS FROM PLATES WEAR TESTS

PA 66 + 30% GF/ 300°C

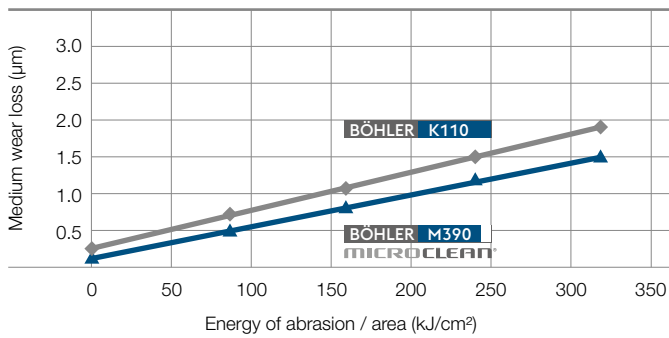

PES + 30% GF/ 400°C

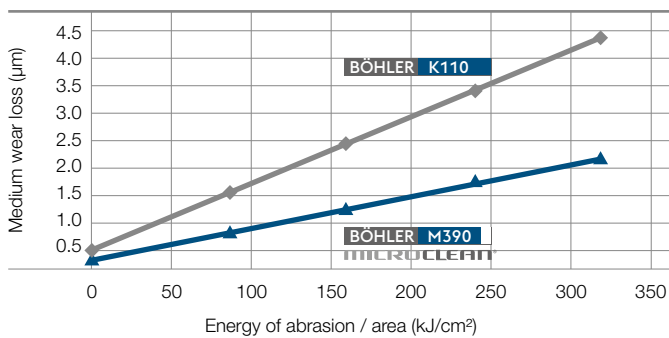

Hardness

Facts

- » Filling materials and additional fibers in various plastic materials have an abrasive effect
- » Together with corrosive media (fission products,...) tribochemical wear system emerges

Abrasion

Free Cr

%	C	Cr	Mo	V	W
K110	1.55	11.80	0.80	0.95	
M390PM	1.90	20.00	1.00	4.00	0.60

Hardness (HRC)

K110*)	58
M390PM	61

Corrosion + Abrasion


Beside wear and corrosion resistance further important factors to choose the right material are:

- » Tool design (complex/simple, deep/shallow cavity, ...)
- » Tool size
- » Surface requirements on the mold


Additional aspects are for instance dimensional stability, edge stability, machinability, ability for coating....

Detailed recommendations have to be checked case by case.

WEAR RESISTANCE WITH PLATE-WEAR TEST

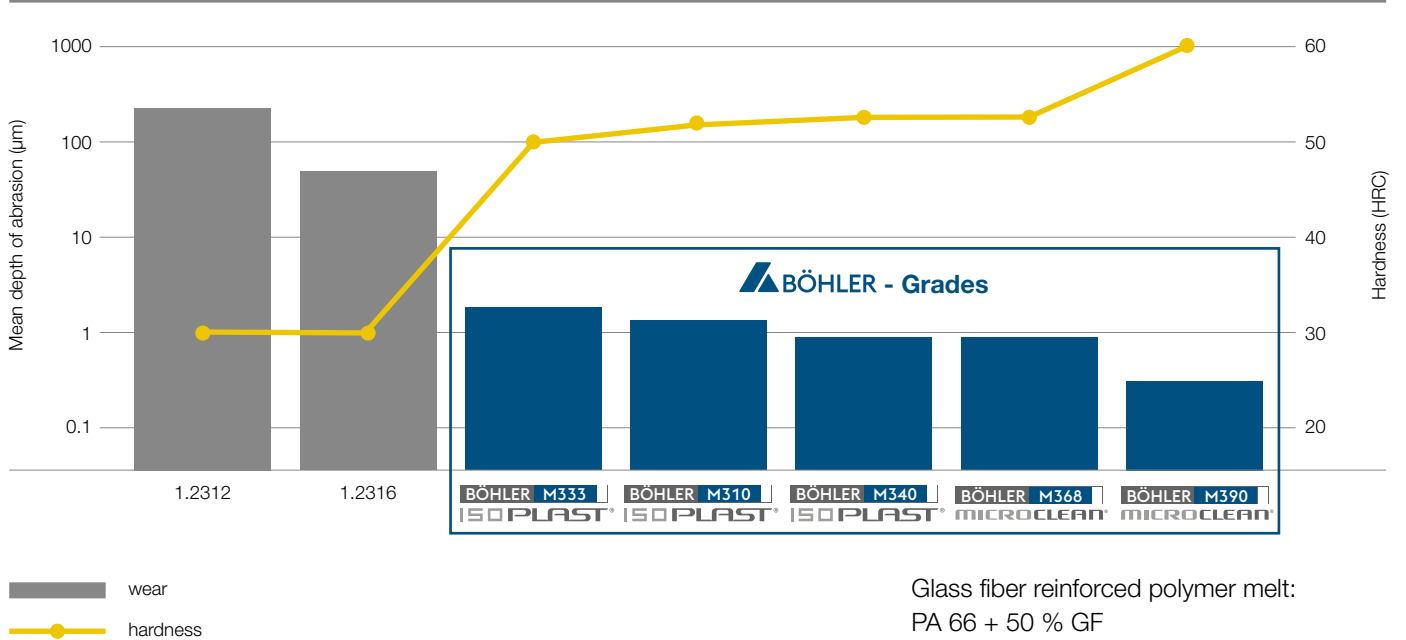


WEAR RESISTANCE WITH PLATE-WEAR TEST – DETAIL

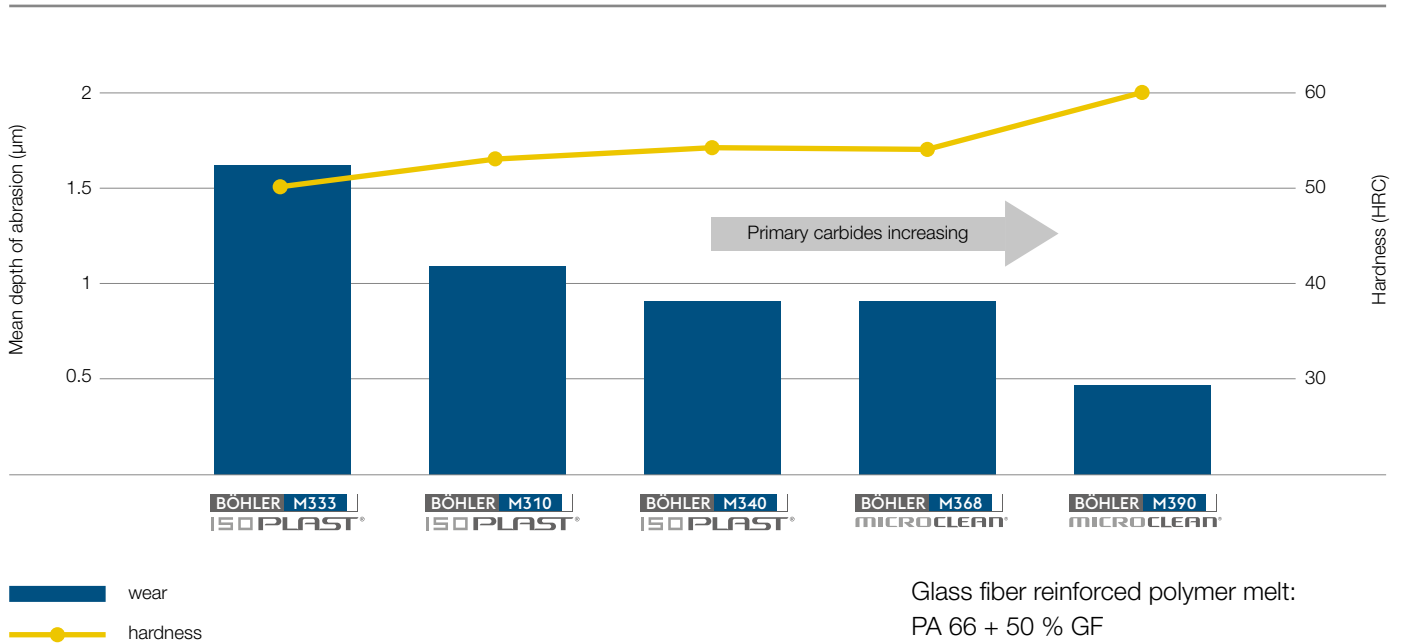

CASE STUDIES

ELECTRICAL COMPONENTS BASE PLATES FOR RELAYS

BOHLER M390
MICROCLEAN

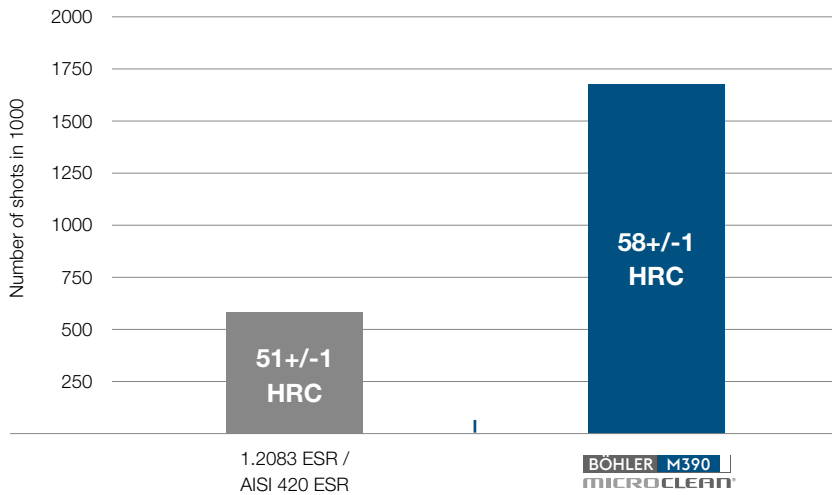


Processed material:

PBT Vestodur X7212 NF + 45% GF

Cause for tool damage: Wear

HOUSEHOLD COMPONENTS GEARS

BOHLER W360
ISOBLOC

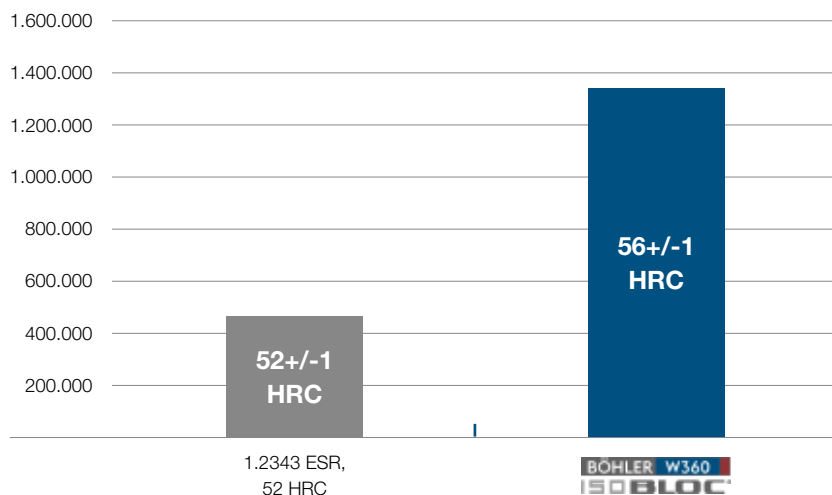

Processed material: PA66 + GF35

Cause for tool damage: Wear



QUALITY LEVELS TECHNOLOGIES

Conventional Production

**THE „STANDARD“ MATERIAL
FOR ORDINARY STRESS,
NORMAL LEVEL WITH:**

Structural conditions


Carbide distribution

Homogeneity

Individual carbides

Degree of purity

Toughness



Microstructure
BÖHLER K110



Electro Slag Remelting Production

ISOPLAST® ISODUR® ISOBLOC®

IMPROVED SERVICE LIFE DUE TO:

Least possible inclusion content

Lower micro and macro segregation

Good homogeneity and a higher degree of purity

Homogenic structure throughout the entire cross-section and bar length

Producing larger bar dimensions at a constant carbide distribution

Uniform dimensional stability

Broad range of application owing to a high degree of toughness

Powder Metallurgical Production

MICROCLEAN®

FOR THE HIGHEST DEMANDS:

Segregation free high performance steel

Finest carbide distribution

Highest metallurgical purity


Isotropic properties

Maximum wear resistance with a simultaneously higher toughness


High degree of hardness

Very good dimensional stability

High compressive strength



Microstructure
BÖHLER K340
in ESR quality



Microstructure
BÖHLER K390
MICROCLEAN



The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.



BÖHLER Tool Steel – exclusively distributed in the USA by EDRO Speciality Steels

BÖHLER Sales Division

EDRO Specialty Steels

20500 Carrey Road

Walnut, California 91789, USA

Phone: (800) 368-3376

Fax: (909) 594-2154

Email: info@edro.com

www.edro.com